

Statistical analysis and optimization of variables affecting the end diameter of AISI 304 steel tube produced by flaring process

Mohammad Isapour Rudy¹, Mahdi Vahdati^{2*}, Mohammad javad Mirnia³

^{1,2} Faculty of Mechanical Engineering, Shahrood University of Technology, Shahrood, Iran

³ Department of Mechanical Engineering, Babol Noshirvani University of Technology, Babol, Iran

ABSTRACT

The flaring of the ends of thin-walled tubes is a subset of single point incremental forming. In this research, the experimental study and statistical analysis of the variables affecting the end diameter of formed tubes were considered. In the present paper, the design of experiment was done based on the response surface methodology. In order to forming the end of AISI 304 steel tube and performing the statistical analysis, process input variables including: tool diameter, tool angular step, tool vertical step and type of lubricant were selected. Then the effect of input variables on the tube end diameter (TED) was analyzed. Also, the TED function was extracted from the input variables in terms of linear, interactive and quadratic expressions, and its competency and adequacy was confirmed. The ANOVA results showed that the expressions of the tool vertical step, tool diameter and the interactive effect of the product of tool diameter and tool angular step are the most effective expressions on the TED. Finally, the optimal combination of process input variables to achieve the maximum of TED was determined using the desirability method, and by running the verification test, the correctness of the regression equation to predict the TED was confirmed.

KEYWORDS

Statistical analysis, Optimization, Steel tube, Flaring process, Single point incremental forming.

* Corresponding Author: vahdati@shahroodut.ac.ir

1. Introduction

Incremental sheet forming (ISF) is recognized as one of the leading methods in the field of rapid prototyping [1]. Single point incremental forming (SPIF) is one of the subsets of the ISF process in which sheet deformation is performed without the need for a die [2]. In this regard, the expansion of the ends of thin-walled tubes using the SPIF process has concerned by the researchers [3]. Cristiano et al [4] numerically and experimentally studied the forming limit of the end of aluminum tube with two methods: pressing and SPIF. They found that the forming limit in the SPIF process is higher than the pressing process. Also, the results showed that a greater of thinning occurs in the tube wall in the SPIF process. Considering the capability of the SPIF process and its advantages compared to traditional forming processes, in this research, the variables affecting the flaring of the ends of AISI 304 steel tubes are studied.

2. Methodology

In this research, incremental forming of the end of the steel tube with an outer diameter of 38 mm (d) with a half angle of 20 degrees (α) and a forming length of 20 mm (L) will be done (Figure 1). Hence, the tube end diameter (TED), denoted by the symbol D in Figure 1, was chosen as the response parameter. The tube thickness is 0.5 mm.

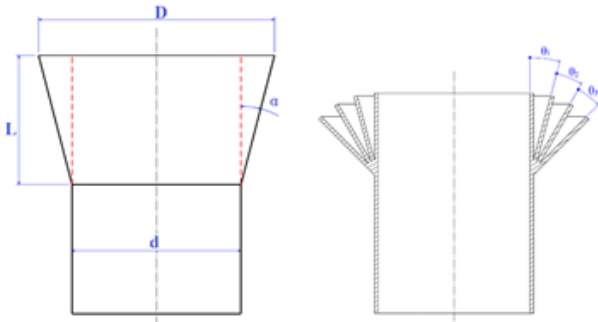


Figure 1. Schematic of tube end flaring

In this research, the input variables of the process along with their change levels were selected according to Table 1.

The experimental tests were designed based on the response surface methodology (RSM) and using the Box-Behnken design (BBD). In this method, the effect of each of the input variables on the response parameter (y) is expressed as equation (1):

$$y = \beta_0 + \sum_{i=1}^k \beta_i x_i + \sum_{i=1}^k \beta_{ii} x_i^2 + \sum_{i,j} \beta_{ij} x_i x_j + \varepsilon \quad (1)$$

Table 1. Experiment factors and their change levels

Variable	Symbol	Unit	-1	0	+1
Tool diameter	D	mm	8	10	12
Tool angular step	A	Degree	4	7	10
Tool vertical step	V	mm	0.2	0.5	0.8
Lubricant type	L	-	Oil	Grease	Graphite

In the above function, β_0 is a constant value, β_i is a linear coefficient, β_{ii} is a quadratic coefficient, β_{ij} is an interactive coefficient, x is the independent variable, k is the number of independent variables and ε is the observed error in the response. The design of experiment was done using Minitab software with 27 runs [5]. The forming of the end of tube was done with spherical-head tools with diameters of 8, 10 and 12 mm. This process was done with a feed rate of 800 mm/min, without spindle rotation and in a spiral path. Figure 2 shows some of the formed samples. The tube end diameter (TED) was measured using a profile projector.



Figure 2. Some of the formed samples

3. Results and Discussion

3.1. Statistical analysis

Analysis of the results is done using analysis of variance (ANOVA). The confidence level was considered equal to 0.05. According to the ANOVA results, it can be seen that the variables of tool diameter (D), tool vertical step (V) and the interactive effect of the product of tool diameter and tool angular step (DA) are effective terms on the response parameter (TED). The regression model of the TED was extracted as coded form according to equation (2):

$$TED = 48.16 + 0.544D - 0.131A - 0.576V + 0.016L - 0.552D^2 + 0.5A^2 - 0.386V^2 + 0.701L^2 - 0.568DA + 0.066DV - 0.046DL - 0.221AV + 0.268AL - 0.184VL \quad (2)$$

Also, with a tool diameter of 12 mm and a vertical step of 0.2 mm, the maximum of TED can be achieved (Figure 3). As can be seen, in small vertical steps due to the continuous movement of materials, a larger diameter is obtained in the expanded section of the tube. Also, increasing the tool diameter and reducing the tool vertical step will lead to a decrease in the spring-back of the tube edges and an increase in the TED.

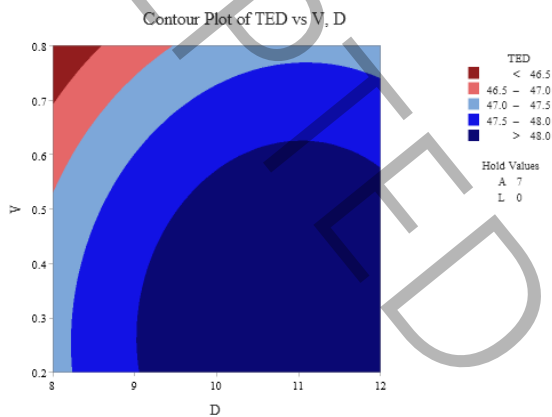


Figure 3. Effect of tool diameter and tool vertical step

3.2. Optimization

In this research, the desirability method was used to optimize the input variables [6]. The objective of the desirability function is to maximize the response parameter (TED). The desirability value obtained from the optimization process was 0.602. The optimal values of the input variables were obtained as follows: tool diameter is equal to 12 mm, angular step is equal to 4 degrees, vertical step is equal to 0.46 mm and oil was chosen as the optimal lubricant.

3.3. Studying the thickness change in the expanded section of the tube

In order to investigate the thickness change in the expanded section of the tube, three samples were selected. The nominal size of the TED is equal to 52.559 mm. The samples were cut longitudinally using a wire-EDM. The thickness of the tubes in the expanded section was measured using a Kroepelin gauge. It was observed that by increasing the forming angle and applying the maximum tensile force, the thinning occurs at the end of the expanded section of the tubes.

4. Conclusion

The important results of this research are summarized as follows:

- The regression model for predicting the tube end diameter (TED) was extracted.
- According to the ANOVA results, the terms affecting the TED are: tool diameter, tool vertical step and the interactive effect of the product of tool diameter and tool angular step.
- The optimal values of the input variables to achieve the maximum of TED were extracted.
- By increasing the tool diameter and decreasing the tool vertical step, a larger diameter is obtained at the end of the tube. Hence, in addition to reducing the spring-back, will cause more thinning in the thickness of the end of the expanded section.

5. References

- [1] M. Vahdati, Finite Element Analysis and Experimental Study of the Ultrasonic Vibration-assisted Single Point Incremental Forming (UVaSPIF) Process, Iranian Journal of Materials Forming, 6 (2) (2019) 30-41.
- [2] M. Vahdati, R.A. Mahdavinejad, S. Amini, Statistical Analysis and Optimization of Factors Affecting the Spring-back Phenomenon in UVaSPIF Process Using Response Surface Methodology, International Journal of Advanced Design and Manufacturing Technology, 8 (1) (2015) 13-23.
- [3] C.P. Nikhare, Y.P. Korkolis, B.L. Kinsey, Formability enhancement in titanium tube-flaring by manipulating the deformation path, Journal of Manufacturing Science and Engineering, 137 (5) (2015) 051006.
- [4] V.A. Cristino, J.P. Magrinho, G. Centeno, M.B. Silva, P.A.F. Martins, Theory of single point incremental forming of tubes, Journal of Materials Processing Technology, 287 (2021) 116659.
- [5] <http://www.minitab.com>
- [6] R.H. Myers, D.C. Montgomery, C.M. Anderson-Cook, Response Surface Methodology: Process and Product Optimization Using Designed Experiments, John Wiley & Sons, ISBN: 978-1-118-91601-8 (2016).