

Investigation on Mechanical Properties of Polyoxymethylene Reinforced by Carbon Nanotube Using Molecular Dynamics

Esmail Zaminpayma¹, Mahnaz Shamshirsaz^{2*}, Payman Nayebi³

¹ Department of Physics, Qazvin Branch, Islamic Azad University, Qazvin, Iran

² New Technologies Research Center, Amirkabir University of Technology, Tehran Polytechnic, 424 Hafez Ave., P.B. 15875-4413, Tehran, Iran

³ Department of Physics, College of Technical and Engineering, Saveh Branch, Islamic Azad University, Saveh, Iran

ABSTRACT

Polyoxymethylene as a thermoplastic or soft plastic material, in addition to its acceptable mechanical strength, has a much lower density comparing to metals. Therefore, it can be a good alternative to non-ferrous metals in the industry. In this study, nanocomposites of this polymer with carbon nanotubes were used to enhance the strength and improve the mechanical properties of the polymer. Experimental analyses of the nanocomposites have the limitations due to the high cost. Therefore, using microscopic scale simulation methods can be a good alternative to study the properties and behavior of these nanocomposites. In this study, the molecular dynamics method is used to simulate the mechanical properties of the nanocomposite. The simulation results obtained in this study show that density and mechanical properties of pure polymer such as Young's modulus, yield stress, and the ultimate stress are consistent with experimental values. Moreover, with temperature increase, these mechanical properties will be reduced. Also, these properties by reinforcing polymer with carbon nanotubes which functionalized with hydroxyl and fluoro groups in a nanocomposite structure can modulate Young's modulus from 41.31 to 44.6% and yield stress from 20 to 80% respectively.

KEYWORDS

Polymer nanocomposite, Carbon nanotube, Molecular Dynamics, Mechanical properties, Polyoxymethylene

* Corresponding Author: Mahnaz Shamshirsaz, Email: shamshir@aut.ac.ir

1. Introduction

Today, composites of polymer and nanomaterials such as graphene and carbon nanotube (CNT) have many applications. Researchers use many simulation methods to study the properties of nanocomposites such as Molecular Dynamics (MD) and Quantum Mechanics (QM) [1-4]. Investigation of the behavior and properties of nanocomposites was first started experimentally but experimental method is limited due to its high cost. Therefore, the use of microscopic scale simulation techniques can be a good solution for studying the properties and behavior of nanocomposites. MD simulation is one of these efficient simulation methods which can be used to investigate the mechanical and thermal properties of nanostructures. MD simulation is a classical physics-based method based on solving Newton's dynamics equation for each particle and studying the time evolution of its system.

Several articles have investigated the properties of polymer nanocomposites reinforced with carbon nanostructures, including graphene and CNT using molecular dynamics simulation. Han et al. [5] used the MD technique to simulate the PMMA and PmPV polymer/CNT composites by using a single wall (10, 10) CNT. Their simulation results showed that the CNTs can mechanically reinforce a polymer matrix, especially in the longitudinal direction of the nanotube. Frankland et al. [6] investigated the effects of the CNT lengths and their discontinuities on the reinforcement of polymer matrix behaviors. The results showed that only the long CNTs could provide a clear reinforcement in the polymer matrix. Nayebi et al. [7] studied the mechanical properties of graphene-polythiophene composite with Reax force field. They found that mechanical characters of tension along the zigzag orientation are higher than the other directions. Also, by increasing the weight concentration of graphene in composite, the Young's modulus and breaking strain increase. They showed that the Young's modulus decreases with increasing temperature. Islam et al. [8] studied the mechanical properties of Polyoxymethylene (POM)/CNT composite. They considered only a simple CNT without any functionalized group in the center of simulation box with Reactive force field. They found that CNT increases the Young's modulus of polymer.

The POM is one of the thermoplastic polymers used in precision parts requiring high stiffness, low friction. In this paper, we study the mechanical properties of POM and functionalized CNT such as hydroxyl (-OH) and fluoro (-F) groups.

2. Simulation Method

Molecular dynamics simulations were performed using LAMMPS software [9] with applying the PCFF force field to investigate the mechanical properties of functionalized CNT reinforced POM nanocomposites. This force field, which is one of the compatible force fields, is often used for molecules with covalent bonds such as organic matter and polymers [10]. Energy statements in this field of energy include the sum of interconnected (valence), merged interactions (cross-term) and nonconnected (non-bond) as follow:

$$E_{total} = E_{valence} + E_{cross-term} + E_{non-bond} \quad (1)$$

The valence interactions are divided into four categories: bond, angle, torsion (dihedral) and out-of-plane angle as follow:

$$E_{valence} = E_{bond} + E_{angle} + E_{torsion} + E_{oop} \quad (2)$$

In order to prepare the structure of the composite, three functionalized CNT were inserted in the POM network in different directions. The boundary conditions of the simulation box were periodic. At first stage, structure is built at very low density. In order to get the experimental density, the structure is pressed at 1 GPa and the 300 K for 1 nanosecond (the compression stage). Then, the system is heated up to 700 K in 1 atm for 1 nanosecond (the heating phase). The compression-heating cycle is repeated five times and then relaxed for 1 nanosecond at 300 K reaching the equilibrium at atmospheric pressure; in order to approach the density to experimental polymer density. The time step was 1 femtosecond and the temperature and pressure were controlled using a noise-hoover thermostat. To obtain the stress-strain curve, the loading mechanism in simulation process was strain loading with a constant rate in one direction.

3. Discussion and Results

Fig.1 a,b,c,d show the POM monomer, POM chain with 100 monomer, CNT with -OH group and CNT with -F group, respectively. Fig. 2 shows the stress-strain curve for pure POM at 100, 200 and 300 K with a strain rate of 10^9 s^{-1} , the simulation box has 10 chains. Table 1 also shows the mechanical characteristics obtained from these graphs, including Young's modulus (slope of the graph in the linear region), yield stress (yield of linear end of the region) and ultimate stress.

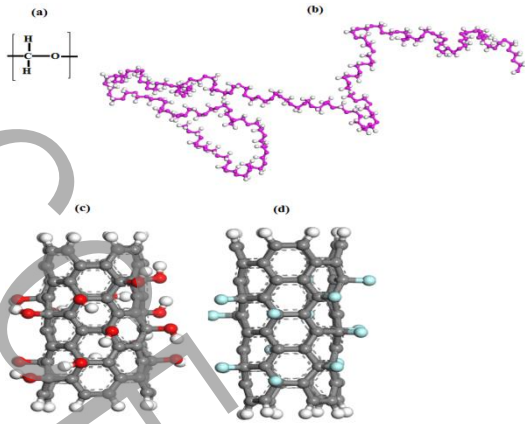


Fig. 1. Structures used in simulation

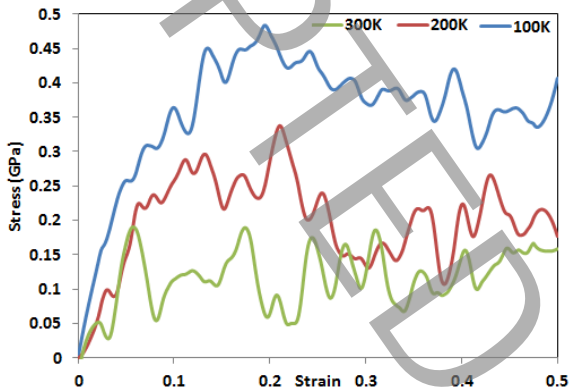


Fig. 2. Stress-strain curves of polymer at three different temperatures 100, 200 and 300 K (rate of 10^9 s^{-1})

As it can be seen, with temperature increase, the mechanical properties will be decreased; this can be due to the material softening as the temperature increases.

Table 1. Young's modulus, yield stress, and ultimate stress of POM polymer

Temperature (K)	Young's Modulus (GPa)	Yield Stress (GPa)	Maximum Stress (GPa)
100	6.68	0.16	0.48
200	3.37	0.10	0.35
300	3.92	0.05	0.19

We added three functionalized CNT with hydroxyl (-OH) and fluoro (-F) groups to simulation box and computed the stress-strain curves at 300 K and rate of 10^9 s^{-1} . Table 2 also shows the mechanical characteristics obtained from these graphs. These results show that composites with functionalized CNT are stronger than without any CNT. In addition, the Young's Modulus of -F group is higher than -OH group because of high electronegativity of -F group related to -OH group.

Table 2. Young's modulus, yield stress and maximum stress composites with functionalized CNT and without CNT

Functionalized	Young's Modulus (GPa)	Yield Stress (GPa)	Ultimate Stress (GPa)
No-CNT	3.92	0.05	0.19
-OH	5.54	0.06	0.20
-F	5.67	0.09	0.19

4. Conclusions

In this paper, mechanical properties of POM/functionalized-CNT by molecular dynamics simulation and applying PCFF force field are investigated. The results show that as the temperature increases, the mechanical properties such as Young's modulus, yield stress and ultimate stress are decreased, which may be due to the softening of the material as the temperature increases. In addition, the Young's Modulus of -F group is higher than -OH group because of high electronegativity of -F group related to -OH group. The simulation results demonstrate that CNT with -OH and -F groups in a nanocomposite structure leads to increasing Young's modulus from 41.31 to 44.6% and yield stress from 20 to 80%.

5. REFERENCES

- [1] Q.H. Zeng, A.B. Yu, G.Q. Lu, Multiscale modeling and simulation of polymer nanocomposites, *Progress in polymer science*, 33(2) (2008) 191-269.
- [2] C.P. Buckley, Elastic constants for an intercalated layered-silicate/polymer nanocomposite using the effective particle concept: A parametric study using numerical and analytical continuum approaches, *Computational Materials Science*, 44(4) (2009) 1332-1343.
- [3] D.-H. Kim, H.-S. Kim, Investigation of hygroscopic and mechanical properties of nanoclay/epoxy system: Molecular dynamics simulations and experiments, *Composites science and technology*, 101 (2014) 110-120.
- [4] E. Harkin-Jones, L. Figiel, P. Spencer, R. Abu-Zurayk, W. Al-Shabib, V. Chan, R. Rajeev, K. Soon, P. Buckley, J. Sweeney, Performance enhancement of polymer nanocomposites via multiscale modelling of processing and properties, *Plastics, rubber and composites*, 37(2-4) (2008) 113-123.
- [5] Y. Han, J. Elliott, Molecular dynamics simulations of the elastic properties of polymer/carbon nanotube

composites, Computational Materials Science, 39(2) (2007) 315-323.

[6] S.J.V. Frankland, A. Caglar, D.W. Brenner, M. Griebel, Molecular simulation of the influence of chemical cross-links on the shear strength of carbon nanotube-polymer interfaces, The Journal of Physical Chemistry B, 106(12) (2002) 3046-3048.

[7] P. Nayebi, E. Zaminpayma, A molecular dynamic simulation study of mechanical properties of graphene-polythiophene composite with Reax force field, Physics Letters A, 380(4) (2016) 628-633.

[8] K. Islam, S. Saha, A.K.M. Masud, Molecular dynamics simulation of the mechanical properties of CNT-polyoxymethylene composite with a reactive forcefield, Molecular Simulation, 46(5) (2020) 380-387.

[9] S. Plimpton, Fast parallel algorithms for short-range molecular dynamics, Journal of computational physics, 117(1) (1995) 1-19.

[10] H. Sun, S.J. Mumby, J.R. Maple, A.T. Hagler, An ab initio CFF93 all-atom force field for polycarbonates,

Journal of the American Chemical Society, 116(7) (1994) 2978-2987.