

Numerical simulation of elastoplastic behavior and damage evolution at various stress triaxiality

Mahdi Ansari¹, Mehdi Ganjiani ^{1*}, Amin Lalegani ¹,

¹ Department of Mechanical Engineering, College of Engineering, University of Tehran, P.O. Box 11155-4563, Tehran, Iran.

ABSTRACT

The theory of continuum damage mechanics with a phenomenological approach is able to simulate phenomena such as soft strain, local necking of materials and their failure. The stress triaxiality defined as the stress state in a material, strongly affect the ductile failure phenomena. In this study, two damage models, Ganjiani and Bonora, are chosen to simulate and compare the elastoplastic behavior as well as damage evolution of some metals. These damage models are sensitive to the stress triaxiality. In order to validate the capability of the models in structural response, the proposed model has been implemented into user-defined subroutines VUMAT in the finite element program ABAQUS/Explicit. For this purpose, the explicit stress integration algorithms of the model have been explained. The model has been validated by comparing the predicted results with experimental data. The simulations are performed for steel 1045, aluminum 2024-T351 and steel HY130. The details of integration algorithm in the framework of explicit scheme are presented. Also the model is developed in the large strain deformation. For determination of the constants in the models, the stress-strain, the damage-strain and the fracture strain-triaxiality curves are used. The predicted curves of load-displacement from simulation have good agreement with corresponding experiment data.

KEYWORDS

Damage mechanics, stress triaxiality, fracture strain, elastoplastic behavior, ductile fracture.

* Corresponding Author: Email: ganjiani@ut.ac.ir

1. Introduction

Continuum Damage Mechanics (CDM) as a phenomenological approach is widely used in a coupled or uncoupled scheme to joint to the (visco) plasticity theory to simulate well the strain softening, damage localization and fracture phenomena in materials [for example 1, 2-4]. Experimental evidences have shown the key factor of stress triaxiality, which relies the mean stress, on fracture strain. Besides that, the stress triaxiality has been found to be not the single factor to affect the ductile damage evolution, especially under shear loading condition. In order to consider the effect of shear loading on the ductile fracture, another key factor as Lode angle parameter was proposed. This parameter is actually related to the third deviatoric stress invariant J_3 . Many ductile fracture models have been proposed in the literature, which used the definition of damage to predict fracture strain [4-10]. The original Gurson–Tvergaard–Needleman (GTN) model [11, 12] predicts no damage change with strain under zero stress triaxiality except when voids are nucleated. On the other hand, this model has the limitations which ignores the fracture mechanism due to shear. Therefore, many authors attempt to modify the limitations of this model.

In this study, two damage models, Ganjiani and Bonora, are chosen to simulate and compare the elastoplastic behavior as well as damage evolution of some metals. The simulations are performed for steel 1045, aluminum 2024-T351 and steel HY130. The details of integration algorithm in the framework of explicit scheme are presented.

2. Methodology

The stress triaxiality η is defined as $\eta = \sigma_m / \sigma_{eq}$ where $\sigma_m = \text{trace}(\boldsymbol{\sigma}) / 3$ is the mean stress.

2.1. Ganjiani model

The model of Ganjiani can be presented as follows:

$$D = \frac{1}{c_d} \operatorname{arctanh} \left\{ \frac{1}{EK_d} \left[1 + c_\eta \ln \left(\frac{1+\eta}{1+\eta_{ref}} \right) \right]^2 \left[R(\varepsilon_{eq}^p) \right]^2 - \frac{Y_0}{K_d} \right\} \quad (1)$$

where $\bar{\varepsilon}^p$ is the equivalent plastic and the parameters E , K_d , c_η and c_θ are material constants and the superscript “ref” refers to the reference test which is used to identify the parameters involved in the model. $R(\varepsilon_{eq}^p)$ is the plastic hardening which is selected as $K[\varepsilon_0 + \varepsilon^p]^n$.

2.2. Bonora model

The model of Bonora can be presented as follows:

$$D = D_{cr} \left\{ 1 - \left[1 - R_\eta^{1-\gamma} \frac{\ln(R_\eta^\beta \varepsilon^p / \varepsilon_{th})}{\ln(\varepsilon_{funi} / \varepsilon_{th})} \right]^\alpha \right\} \quad (2)$$

In which The $R_\eta = \frac{2}{3}(1+\nu) + 3(1-2\nu)\eta^2$ is the function that accounts for stress triaxiality effects. S_0 , γ , α , β are constants. ε_{th} is thresholds strain and ε_{funi} is the fracture strain at uniaxial tension test.

3. Discussion and Results

The simulations are performed for steel 1045, aluminum 2024-T351 and steel HY130. The material properties is calibrated. The tension test are simulated for steel 1045 and aluminum 2024-T351, and the three-point bending test is simulated for steel HY130. The force-displacement of these simulation are presented in figures 1 to 3.

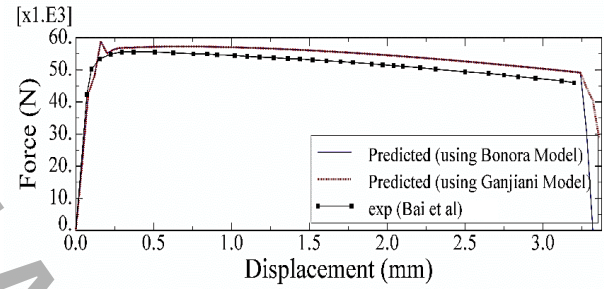


Figure 1: The comparison of force-displacement between simulation and the result of ref. [34] for steel 1045.

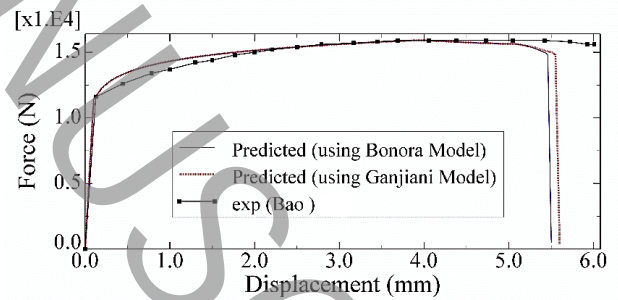


Figure 1: The comparison of force-displacement between simulation and the result of ref. [44] for aluminum 2024-T351

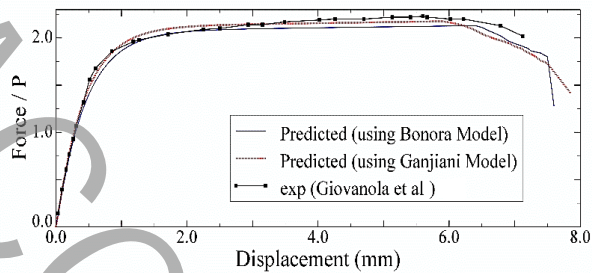


Figure 1: The comparison of force-displacement between simulation and the result of ref. [52] for steel HY130.

The finite element analysis is carried out to show the capability of the model at structural scale. As indicated in these figures, the predicted results have good agreement

4. Conclusions

In this paper, a fracture model has been presented in framework of Continuum Damage Mechanics. Two damage models, Ganjiani and Bonora, are chosen to simulate. The simulations are performed for steel 1045, aluminum 2024-T351 and steel HY130. The details of integration algorithm in the framework of explicit scheme are presented. The curves of load-displacement from simulation have good agreement with corresponding experiment ones

5. References

- [1] R. Vignjevic, N. Djordjevic, T. De Vuyst, S. Gemkow, Modelling of strain softening materials based on equivalent damage force, *Computer Methods in Applied Mechanics and Engineering*, 335 (2018) 52-68.
- [2] Y. Zhu, M.D. Engelhardt, A nonlocal triaxiality and shear dependent continuum damage model for finite strain elastoplasticity, *European Journal of Mechanics-A/Solids*, 71 (2018) 16-33.
- [3] F.A. McClintock, A criterion for ductile fracture by the growth of holes, *Journal of applied mechanics*, 35(2) (1968) 363-371.
- [4] J.R. Rice, D.M. Tracey, On the ductile enlargement of voids in triaxial stress fields, *Journal of the Mechanics and Physics of Solids*, 17(3) (1969) 201-217.
- [5] G.R. Johnson, W.H. Cook, Fracture characteristics of three metals subjected to various strains, strain rates, temperatures and pressures, *Engineering fracture mechanics*, 21(1) (1985) 31-48.
- [6] L. Xue, Damage accumulation and fracture initiation in uncracked ductile solids subject to triaxial loading, *International journal of solids and structures*, 44(16) (2007) 5163-5181.
- [7] M. Wilkins, R. Streit, J. Reaugh, Cumulative-strain-damage model of ductile fracture: simulation and prediction of engineering fracture tests, Lawrence Livermore National Lab., CA (USA); Science Applications, Inc., San Leandro, 1980.
- [8] M. Cockcroft, D. Latham, Ductility and the workability of metals, *Journal of the Institute of Metals*, 96(1) (1968) 33-39.
- [9] A.S. Khan, H. Liu, A new approach for ductile fracture prediction on Al 2024-T351 alloy, *International Journal of Plasticity*, 35 (2012) 1-12.
- [10] L. Xue, T. Wierzbicki, Ductile fracture initiation and propagation modeling using damage plasticity theory, *Engineering Fracture Mechanics*, 75(11) (2008) 3276-3293.
- [11] A.L. Gurson, Continuum theory of ductile rupture by void nucleation and growth: Part I—Yield criteria and flow rules for porous ductile media, *Journal of Engineering Materials and Technology*, 99(1) (1977) 2-15.
- [12] V. Tvergaard, A. Needleman, Analysis of the cup-cone fracture in a round tensile bar, *Acta metallurgica*, 32(1) (1984) 157-169.
- [13] K. Nahshon, J. Hutchinson, Modification of the Gurson model for shear failure, *European Journal of Mechanics-A/Solids*, 27(1) (2008) 1-17.
- [14] K.L. Nielsen, V. Tvergaard, Effect of a shear modified Gurson model on damage development in a FSW tensile specimen, *International Journal of Solids and Structures*, 46(3-4) (2009) 587-601.
- [15] L. Xue, Constitutive modeling of void shearing effect in ductile fracture of porous materials, *Engineering Fracture Mechanics*, 75(11) (2008) 3343-3366.
- [16] L. Malcher, F.A. Pires, J.C. De Sá, An extended GTN model for ductile fracture under high and low stress triaxiality, *International Journal of Plasticity*, 54 (2014) 193-228.
- [17] J. Zhou, X. Gao, J.C. Sobotka, B.A. Webler, B.V. Cockeram, On the extension of the Gurson-type porous plasticity models for prediction of ductile fracture under shear-dominated conditions, *International Journal of Solids and Structures*, 51(18) (2014) 3273-3291.
- [18] J. Lemaitre, A continuous damage mechanics model for ductile fracture, *Journal of Engineering Materials and Technology*, 107 (1985) 83-89.
- [19] W. Jiang, Y. Li, J. Su, Modified GTN model for a broad range of stress states and application to ductile fracture, *European Journal of Mechanics-A/Solids*, 57 (2016) 132-148.