



Experimental study of machining residual stresses in plasma-assisted turning process

M. Khajezadeh* , M. R. Razfar

Department of Mechanical Engineering, Amirkabir University of Technology, Tehran, Iran

ABSTRACT: The possibility of workpiece deformation after or during machining due to residual stresses is of crucial importance in precise components. These stresses are induced mainly due to plastic deformation or heat generation during the metal cutting process. Therefore, the magnitude of machining residual stresses is affected by mechanical and thermal stresses. Mechanical stresses depend on the cutting forces and thermal stresses originate from the magnitude of heat generation during cutting action. Therefore, it is expected that machining processes with lower cutting forces and cutting temperatures, will induce lower machining residual stresses as well. Plasma assisted machining is a process that uses a heat source to increase workpiece local temperature and thereby decrease the strength of the material which is to be removed; therefore lower values of cutting forces, temperatures, and residual stresses are expected. In this research work, the effects of undeformed chip temperature, cutting speed, and feed have been investigated on the machining induced residual stresses in the plasma-assisted orthogonal turning of AISI 4140. According to the achieved results, undeformed chip temperature is the most effective parameter on machining residual stresses and by increasing this parameter from 75 to 220°C, machining induced surface residual stresses became more compressive averagely by 85.30%.

Review History:

Received: Dec. 19, 2019
Revised: Mar. 14, 2020
Accepted: May, 03, 2020
Available Online: May, 09, 202

Keywords:

Residual stress
Heat assisted machining
Plasma
Cutting forces
X-ray diffraction.

1- 1. Introduction

Heat assisted machining is a process that uses a heat source, Fig. 1(a), to increase workpiece local temperature and thereby decrease the strength of the material which is to be removed; therefore lower values of cutting forces and cutting temperatures are expected [1-3]. Farahnakian et al. studied plasma-assisted machining of hardened steel 4140. They found that if the heat source is controlled so that the undeformed chip temperature could vary between 150 and 390°C, the main component of cutting force will be reduced by 27% compared to traditional machining [2]. On the other hand, cutting forces and cutting temperature are the main causes of machining residual stresses; therefore, it is expected that applying a concentrated local heat source will also lead to a lower level of machining-induced residual stresses. For instance, Balba et al. studied residual stress in Inconel 18 alloy by developing an SPH model. They showed that in contrary to traditional machining which produces tensile residual stress on the workpiece surface, laser-assisted machining, in the selected range of machining parameters, will result in compressive residual stresses [3]. However, they did not present any experimental data to verify their claim and did not address the effect of heat source parameters or undeformed chip temperature on the type and magnitude of machining residual stresses.

In this research work, the effect of undeformed chip temperature, cutting speed, and feed has been investigated on machining induced surface residual stresses in the plasma-assisted turning of AISI 4140.


2- Methodology

2.1. Plasma assisted machining

The plasma-assisted machining process is schematically shown in Fig. 1(a). Consider an element of workpiece located on the outer surface of the workpiece at point A. This element comes close to the heat source due to workpiece rotation and its temperature rises rapidly, Fig. 1(b). When this element reaches the location of the heat source (point B), it will achieve its maximum temperature. By moving away from the heat source, the temperature of the element begins to decrease due to heat transfer to the surrounding environment (mainly due to thermal conduction and convection). Finally, the element is exposed to the cutting tool at point C. The temperature of the element at this point is a good approximation of undeformed chip temperature (i.e. T_{uch}).

Controlling T_{uch} is one of the most important challenges in the heat-assisted machining process; if this temperature is below a certain limit, the material flow stress will not change significantly, therefore, reduction in cutting forces can't be expected. On the other hand, if the temperature exceeds the

*Corresponding author's email: mo.khajezadeh@aut.ac.ir



temperature of the re-crystallization, the unwanted changes in the microstructure of the machined workpiece will be inevitable. Therefore, in order to achieve the required levels of T_{uch} , it is necessary to determine the temperature distribution of the workpiece so that the plasma source current can be adjusted according to the required T_{uch} . To achieve this goal, a mathematical model was developed to predict the effect of feed, cutting speed, and electrical current density on the value of undeformed chip temperature.

2.2 Experimental setup

In this research, tests were done by a universal machine (TN50BR). Plasma-assisted machining equipment included an inverter and a plasma torch from Saba electric Company. The model of the applied generator was CUT 121 which supplied electric current in the range of 20-120 A and in voltage of 70 V. The machining setup is shown in Fig. 2.

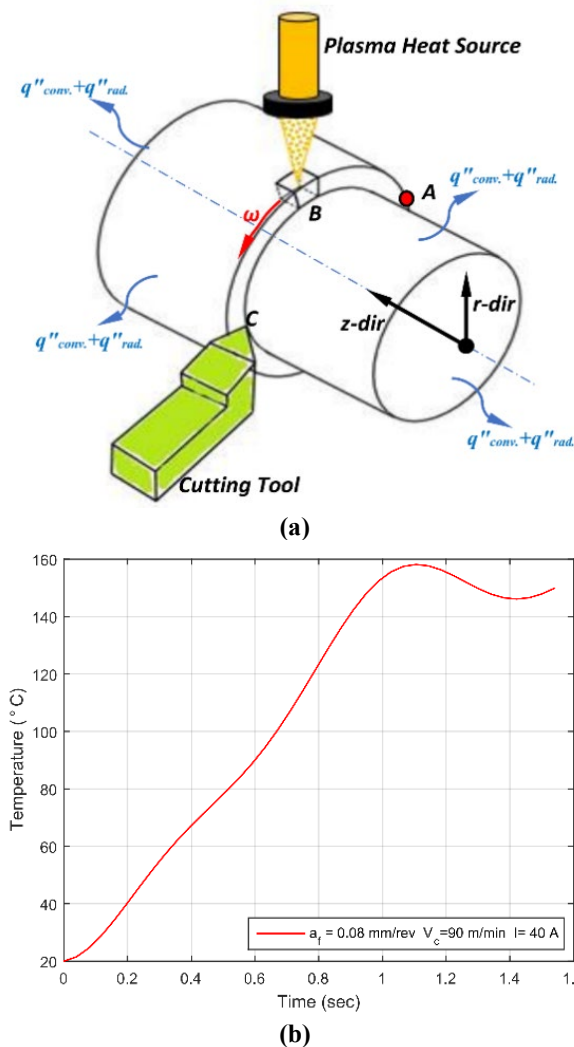


Fig. 1. Modeling of undeformed chip temperature in heat-assisted turning [1] (a) heat transfer problem boundary condition, (b) undeformed chip temperature variations, and (c) effect of feed, cutting speed, and electrical current intensity on undeformed

Table 4. Variables and their levels.

Parameter	1	2	3	4
Cutting Speed (m/min)	60	90	120	-
Feed (mm/rev)	0.08	0.14	-	-
Undeformed Chip Temperature ($^{\circ}C$)	20	75	150	200

2.3. Design of Experiments (DOE)

In this study, to conduct the experiments and investigate the effect of machining parameters (including cutting speed and feed) and undeformed chip temperature on machining induced residual stresses, the full factorial method was implemented. Finally, 24 experiments were defined. Parameters and their levels are presented in Table 1.

3- Results and Discussion

-The results of surface residual stresses measurement in plasma-assisted turning show that by increasing T_{uch} , machining induced residual stress reduces and becomes more compressive, Fig. 3(a). Reduction of material flow stress due to increased temperature caused by plasma source is the key point regarding the ability of the laser-assisted process to make machining-induced residual stresses more compressive. In the present study, increasing T_{uch} from 75 to 220 $^{\circ}C$ resulted in 85.3% increase in compressive residual stress due to lower flow stress.

In the constant value of T_{uch} , increasing cutting speed resulted in more tensile residual stresses mainly due to higher heat generation, Fig. 3(a); for example, it is observed that at $T_{uch} = 75^{\circ}C$, increasing cutting speed from 60 to 120 m/min made machining induced residual stresses more tensile by about 50.00%.

Increasing feed will make machining induced residual stresses more tensile in both traditional and plasma-assisted machining, Fig. 3(b); increasing feed will increase the undeformed chip cross-section and thereby cutting forces. Therefore, the amount of heat generation in cutting regions will increase. Generating more heat during cutting action will lead to an increase in tensile stresses and reduces the compressive residual stresses; for example, increasing feed from 0.08 to 0.14 mm/rev made machining induced residual

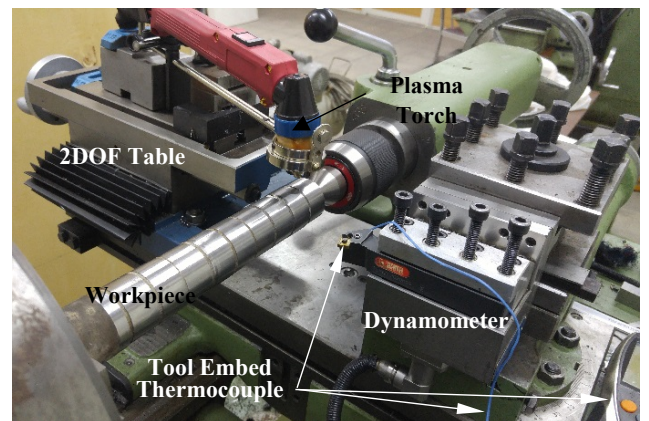


Fig. 2. Experimental setup of plasma-assisted machining.

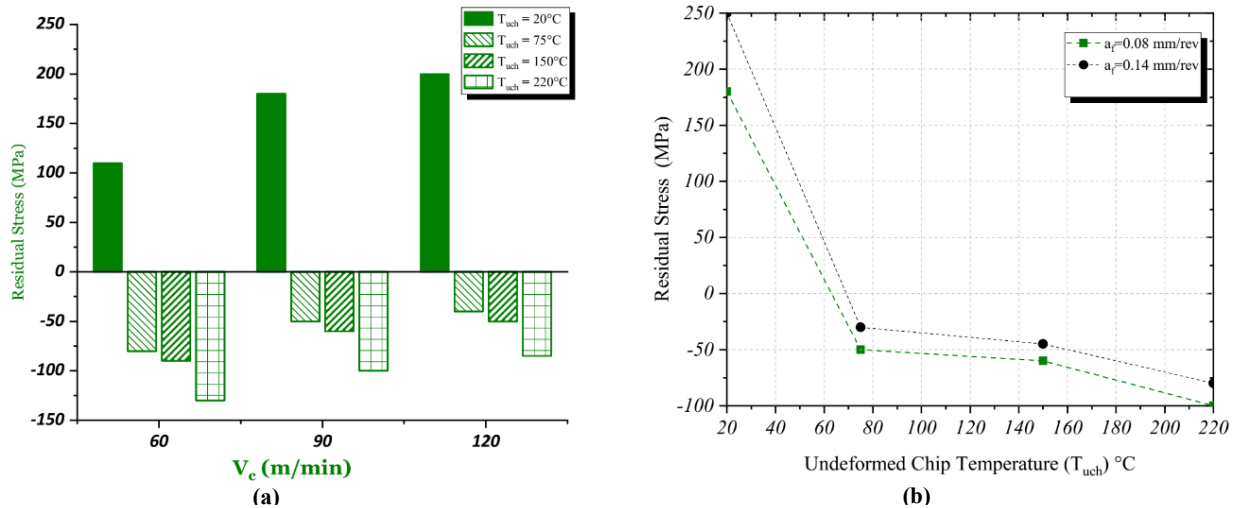


Fig. 3. The effect of cutting parameters and undeformed chip temperature on residual stress (a) $a_f = 0.08$ mm/rev, (b) $V_c = 90$ m/min.

stresses more tensile; this increase in tensile stresses is about 38.9% in traditional cutting while this increase was about 28.34% in case of plasma-assisted machining.

As mentioned above, increasing cutting speed and feed will make machining induced residual stresses more tensile but plasma-assisted machining, attenuates this phenomenon; for example in Fig. 3(b), it is observed that at $T_{uch} = 75^\circ\text{C}$, increasing feed from 0.08 to 0.14 mm/rev made machining induced residual stresses more tensile by about 40.00%; but at $T_{uch} = 150^\circ\text{C}$ and 220°C , the same increase in the feed will respectively make machining induced residual stresses more tensile by about 25 and 20%.

4- Conclusions

According to the achieved results, in plasma-assisted turning of AISI 4140, in the selected range of machining parameters, by increasing undeformed chip temperature from

75 to 220°C , machining induced surface residual stresses became more compressive averagely by 85.30%

Reference

- [1] M.M. Kashani, M.R. Movahhedy, M.T. Ahmadian, R.S. Razavi, In-process Determination of Laser Beam Absorption Coefficient for Laser-Assisted Turning Processes, *International Journal of Advanced Manufacturing Technology*, 92 (2017) 2929-2938.
- [2] M. Frahnakian, M.R. Razfar, Experimental Study on Hybrid Ultrasonic and Plasma Aided Turning of Hardened Steel AISI 4140, *Materials and Manufacturing Processes*, 29 (2014) 550-556.
- [3] M.A. Balbaa, M.N.A. Nasr, H.A. Elgamal, Sensitivity Analysis on the Effect of Laser Power on Residual Stresses when Laser-Assisted Machining AISI 4340, *Procedia CIRP*, 58 (2017) 31-36.

HOW TO CITE THIS ARTICLE

M. Khajezadeh, M.R. Razfar, *Experimental study of machining residual stresses in plasma-assisted turning process*, *Amirkabir J. Mech. Eng.*, 53(4) (2021) 563-566.

DOI: 10.22060/mej.2020.17565.6619



